

Chemical Resistance



For a lifetime of protection.

LEGEND

- 1 immersion, constant flow or vapor
- 2 incidental spill or splash
- 3 fumes only
- NR not recommended
- Contact Raven for more information

This guide is intended as an aid in determining potential use of AquataPoxy, Raven, and AquataFlex products as protective coatings against chemical exposure. Each application should be evaluated according to its own conditions.

| | AquataPoxy | | | | | Raven | | | | | AquataFlex | | |
|--------------------------------|------------|----|-----|-----|----|-------|-----|------|-----|-----|------------|-----|-----|
| | A6 | A7 | A10 | A61 | HB | 404 | 405 | 400S | 415 | 470 | F-1 | F-2 | F-3 |
| Acetic Acid, 5% | NR | NR | NR | -- | 2 | 2 | 2 | 1 | 2 | 1 | 2 | 2 | 2 |
| Acetic Acid, 10% | NR | NR | NR | -- | NR | NR | 3 | 1 | 2 | 1 | NR | NR | NR |
| Acetic Acid, 20% | NR | NR | NR | -- | NR | NR | 3 | 2 | 2 | 2 | NR | NR | NR |
| Acetone | 2 | 2 | NR | 2 | -- | 2 | 2 | 2 | 2 | 1 | 2 | 2 | 2 |
| Ammonium Hydroxide, 1% | 1 | 1 | -- | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Ammonium Hydroxide, 5% | 1 | 1 | -- | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 | 2 | 2 |
| Benzene | 2 | 2 | -- | 2 | 2 | 2 | 2 | 2 | 2 | 1 | 2 | 2 | 2 |
| Bleach | 1 | -- | -- | 1 | 1 | -- | 1 | 1 | -- | 1 | 2 | 2 | 2 |
| Chromic Acid, 15% | -- | -- | -- | -- | -- | -- | -- | 2 | -- | 1 | -- | -- | -- |
| Citric Acid, 10% | 1 | 2 | -- | 1 | 1 | 1 | 1 | 1 | 1 | 1 | -- | -- | -- |
| Deionized Water | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 |
| Detergent Solution (0.025%) | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 |
| Distilled Water | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 |
| Ethanol | 1 | 2 | -- | 2 | -- | 1 | 2 | 1 | -- | 2 | 2 | 2 | 2 |
| Ferric Chloride, 1% | 1 | 2 | -- | 1 | 1 | 1 | 1 | 1 | 1 | 1 | -- | -- | -- |
| Ferric Sulfate, 10% | 1 | 2 | -- | 1 | -- | 1 | 1 | 1 | -- | -- | -- | -- | -- |
| Gasoline, Jet Fuel | 1 | -- | -- | -- | 2 | -- | -- | -- | -- | -- | 2 | 2 | 2 |
| Gasoline, Unleaded | 1 | 2 | -- | -- | 2 | 1 | 1 | 1 | -- | -- | 2 | 2 | 2 |
| Grape Juice | 2 | -- | -- | -- | 2 | 2 | 2 | -- | -- | -- | -- | -- | -- |
| Heptane | 1 | -- | -- | -- | 2 | 1 | 1 | -- | -- | -- | -- | -- | -- |
| Hexane | 1 | -- | -- | -- | 2 | 1 | 1 | -- | -- | -- | -- | -- | -- |
| Hydraulic Fluid | 1 | 2 | -- | -- | -- | 1 | 1 | 1 | 1 | 1 | 2 | 2 | 2 |
| Hydrochloric Acid, 10% | 2 | 2 | 3 | 2 | 2 | 1 | 1 | 1 | 2 | 1 | -- | -- | -- |
| Hydrochloric Acid, 20% | 2 | 2 | -- | -- | -- | 2 | 2 | 1 | -- | 1 | -- | -- | -- |
| Hydrochloric Acid, 37% | -- | -- | -- | -- | -- | -- | 2 | 1 | -- | 1 | -- | -- | -- |
| Hydrogen Peroxide Solution, 3% | 1 | -- | -- | -- | -- | 1 | 1 | -- | -- | -- | -- | -- | -- |
| Kerosene | 1 | -- | -- | 1 | 2 | 1 | 1 | 1 | -- | -- | 2 | 2 | 2 |
| Lactic Acid, 10% | 2 | -- | -- | -- | -- | 2 | 2 | 1 | -- | 2 | NR | NR | NR |
| Lactic Acid, 5% | 1 | -- | -- | -- | -- | 1 | 1 | 1 | -- | 2 | 2 | 2 | 2 |
| Methanol | 2 | -- | -- | 2 | -- | -- | 2 | 2 | -- | 1 | NR | NR | NR |

Chemical Resistance



For a lifetime of protection.

LEGEND

- 1 immersion, constant flow or vapor
- 2 incidental spill or splash
- 3 fumes only
- NR not recommended
- Contact Raven for more information

This guide is intended as an aid in determining potential use of AquataPoxy, Raven, and AquataFlex products as protective coatings against chemical exposure. Each application should be evaluated according to its own conditions.

| | AquataPoxy | | | | | Raven | | | | | AquataFlex | | |
|----------------------------------|------------|----|-----|-----|----|-------|-----|------|-----|-----|------------|-----|-----|
| | A6 | A7 | A10 | A61 | HB | 404 | 405 | 400S | 415 | 470 | F-1 | F-2 | F-3 |
| Methylene Chloride | -- | -- | -- | -- | -- | -- | NR | 2 | -- | 1 | -- | -- | -- |
| Methyl-Ethyl Ketone | 2 | 2 | NR | 2 | -- | 2 | 2 | 2 | 2 | 1 | 2 | 2 | 2 |
| Mineral Spirits | 1 | -- | -- | -- | 2 | 1 | -- | -- | -- | 1 | 2 | 2 | 2 |
| Nitric Acid, 5% | 2 | 2 | -- | 2 | -- | -- | 1 | 1 | -- | 1 | -- | -- | -- |
| Nitric Acid, 10% | 2 | 2 | -- | -- | -- | -- | 1 | 1 | -- | 2 | NR | NR | NR |
| Nitric Acid, 40% | -- | -- | -- | -- | -- | -- | -- | 2 | -- | 3 | NR | NR | NR |
| Oil, Motor | 1 | -- | -- | 1 | 1 | 1 | 1 | -- | -- | 1 | 2 | 2 | 2 |
| Oil, Vegetable | 1 | -- | -- | 1 | 1 | 1 | 1 | -- | -- | 1 | 1 | 1 | 2 |
| Oleic Acid | -- | -- | -- | -- | -- | -- | 1 | 1 | -- | 1 | -- | -- | -- |
| Phenol Solution, 5% | -- | -- | -- | -- | -- | -- | -- | -- | -- | 1 | -- | -- | -- |
| Phosphoric Acid, 10% | 3 | NR | -- | -- | 2 | -- | 1 | 1 | -- | 1 | NR | NR | NR |
| Phosphoric Acid, 85% | NR | NR | -- | -- | NR | -- | 2 | 1 | -- | 2 | NR | NR | NR |
| Potassium Hydroxide, 10% | 1 | 1 | -- | 1 | 1 | 1 | 1 | 1 | -- | 1 | 2 | 2 | 2 |
| Salt Brine | 1 | 1 | 2 | 1 | 1 | 1 | 1 | -- | -- | 1 | 1 | 1 | 2 |
| Skydrol | 1 | -- | -- | -- | 1 | -- | 1 | 1 | -- | 1 | -- | -- | -- |
| Soap Solution, 1% | 1 | 1 | 2 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 |
| Sodium Chloride | 1 | 1 | 2 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Sodium Hydroxide Solution, 10% | 1 | 1 | -- | 2 | 1 | 1 | 1 | 1 | -- | 1 | 2 | 2 | 2 |
| Sodium Hydroxide Solution, 50% | -- | -- | -- | -- | 2 | -- | 2 | 1 | -- | 2 | -- | -- | -- |
| Sodium Hypochlorite Solution, 3% | 2 | NR | -- | 2 | 2 | 1 | 1 | 1 | -- | 1 | -- | -- | -- |
| Sulfuric Acid, 10% | 1 | 2 | 2 | 2 | 1 | 1 | 1 | 1 | -- | 1 | 2 | 2 | 2 |
| Sulfuric Acid, 25% | 2 | 2 | -- | 2 | 2 | 1 | 1 | 1 | -- | 1 | NR | NR | NR |
| Sulfuric Acid, 50% | NR | -- | -- | -- | NR | -- | -- | 1 | -- | 1 | NR | NR | NR |
| Sulfuric Acid, 98% | NR | -- | -- | -- | NR | -- | NR | 1 | -- | 2 | NR | NR | NR |
| Tetrachloroethane | 2 | -- | -- | -- | -- | -- | -- | 2 | -- | 1 | -- | -- | -- |
| Toluene | 2 | -- | 3 | 2 | -- | -- | 2 | 2 | -- | 1 | -- | -- | -- |
| Trichlorethane | 2 | -- | -- | -- | -- | -- | -- | -- | -- | 1 | -- | -- | -- |
| Water, distilled | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 2 |
| Xylene | 1 | -- | -- | 2 | 2 | -- | 1 | 2 | -- | 1 | 2 | NR | NR |



SHERRY Laboratories

Testing Today - Protecting Tomorrow[®]

Tulsa Materials
3100 North Hemlock Circle
Broken Arrow, OK 74012-1115 USA

Tel: 918-258-6066
800-982-8378
Fax: 918-258-1154

LABORATORY REPORT

Attn: David Stanley
Cohesant Materials, Inc.
13105 East 61st Street South, Suite A
Tulsa, OK 74012

Report No.: 06080703-003 v2-Amended
Date Received: 8/23/2006
Date Reported: 9/01/2006
P.O. No.: 314940

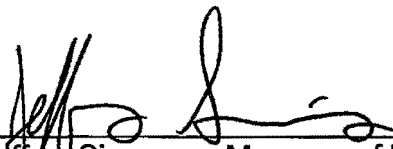
Sample Description: Raven 405

COMPRESSION TEST (ASTM D 695-02a)

Specimen preparation: Cylinders, tested as submitted
Pre-test Conditioning: None (waived)

| Specimen Number | Diameter (inches) | Area (Sq. in) | Peak Load (lbs) | Peak Stress (psi) |
|-----------------|-------------------|---------------|-----------------|-------------------|
| 1 | 0.607 | 0.289 | 5,349 | 18,500 |
| 2 | 0.608 | 0.290 | 5,453 | 18,800 |
| 3 | 0.606 | 0.288 | 5,486 | 19,000 |
| 4 | 0.607 | 0.289 | 5,531 | 19,100 |
| 5 | 0.607 | 0.289 | 5,523 | 19,100 |
| 6 | 0.606 | 0.288 | 5,564 | 19,300 |
| Average | 0.607 | 0.289 | 5,484 | 19,000 |

¹Amended-Sample and page number, 9/7/06.

Approved by: 
Jeffrey Simmons, Manager of Mechanical Testing
Sherry Laboratories

Test results relate only to the items tested. This document shall not be reproduced, except in full, without the written approval of Sherry Laboratories. The recording of false, fictitious, or fraudulent statements or entries on this document may be a punishable offense under federal and state law. The electronic transmittal of a report on services provided by Sherry Laboratories is at the request of the client. The transmittal is NOT the official report of Sherry Laboratories, but is provided for the convenience of the recipient. Sherry Laboratories is not liable for any degradation or changes in information in the transmittal. The official report of Sherry Laboratories will be provided on Sherry Laboratories letterhead in hard copy form and shall control for all purposes.



SHERRY Laboratories

Testing Today - Protecting Tomorrow[®]

Tulsa Materials
3100 North Hemlock Circle
Broken Arrow, OK 74012-1115 USA

Tel: 918-258-6066
800-982-8378
Fax: 918-258-1154

LABORATORY REPORT

Attn: David Stanley
Cohesant Materials, Inc.
13105 East 61st Street South, Suite A
Tulsa, OK 74012

Report No.: 06080703-002 v2-Corrected
Date Received: 8/23/2006
Date Reported: 9/01/2006
P.O. No.: 314940

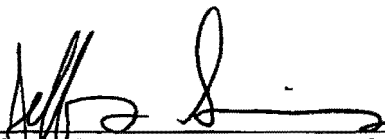
Sample Description: Raven 405

FLEXURAL TEST (ASTM D 790-03)

Specimen preparation: Tested as submitted
Pre-test Conditioning: None (waived)
Span: 2 inches
Test Temperature: 25C
Test Rate: 0.1 in/min

| Specimen Number | Width (in.) | Thickness (in.) | Peak Load (lbs.) | Peak Stress ¹ (psi) | Modulus ¹ (psi) |
|-----------------|--------------|-----------------|------------------|--------------------------------|----------------------------|
| 1 | 0.487 | 0.093 | 19.67 | 14,000 | 726,000 |
| 2 | 0.486 | 0.096 | 21.96 | 14,700 | 750,300 |
| 3 | 0.487 | 0.097 | 22.21 | 14,500 | 731,000 |
| 4 | 0.490 | 0.095 | 19.68 | 13,300 | 716,000 |
| 5 | 0.488 | 0.100 | 24.36 | 14,900 | 724,000 |
| 6 | 0.491 | 0.098 | 23.90 | 15,200 | 717,000 |
| Average | 0.488 | 0.965 | 21.96 | 14,400 | 727,000 |

¹Corrected-Test results, sample and page number, 9/7/06.

Approved by: 
Jeffrey Simmons, Manager of Mechanical Testing
Sherry Laboratories

Test results relate only to the items tested. This document shall not be reproduced, except in full, without the written approval of Sherry Laboratories. The recording of false, fictitious, or fraudulent statements or entries on this document may be a punishable offense under federal and state law. The electronic transmittal of a report on services provided by Sherry Laboratories is at the request of the client. The transmittal is NOT the official report of Sherry Laboratories, but is provided for the convenience of the recipient. Sherry Laboratories is not liable for any degradation or changes in information in the transmittal. The official report of Sherry Laboratories will be provided on Sherry Laboratories letterhead in hard copy form and shall control for all purposes.



SHERRY Laboratories

Testing Today - Protecting Tomorrow*

Tulsa Materials
3100 North Hemlock Circle
Broken Arrow, OK 74012-1115 USA

Tel: 918-258-6066
800-982-8378
Fax: 918-258-1154

LABORATORY REPORT

Attn: David Stanley
Cohesant Materials, Inc.
13105 East 61st Street South, Suite A
Tulsa, OK 74012

Report No.: 06080703-001 v2-Corrected
Date Received: 8/23/2006
Date Reported: 9/01/2006
P.O. No.: 314940

Sample Description: Raven 405

TENSILE TEST (ASTM D 638-03)

Specimen preparation: Tested as submitted
Pre-test Conditioning: None (waived)

| Specimen Number | Width (inches) | Thickness (inches) | Area (Sq. in) | Peak Load (lbs) | Peak Stress (psi) | Elongation ¹ (%) |
|-----------------|----------------|--------------------|---------------|-----------------|-------------------|-----------------------------|
| 1 | 0.486 | 0.095 | 0.0462 | 354 | 7,670 | 1.4 |
| 2 | 0.485 | 0.096 | 0.0466 | 377 | 8,100 | 1.5 |
| 3 | 0.486 | 0.101 | 0.0491 | 413 | 8,400 | 1.6 |
| 4 | 0.488 | 0.095 | 0.0464 | 354 | 7,600 | 1.4 |
| 5 | 0.486 | 0.093 | 0.0452 | 382 | 8,400 | 1.8 |
| 6 | 0.487 | 0.099 | 0.0482 | 416 | 8,600 | 1.6 |
| Average | 0.486 | 0.096 | 0.0470 | 383 | 8,200 | 1.6 |

¹Corrected-Test results, sample and page number, 9/7/06.

Approved by:

Jeffrey Simmons, Manager of Mechanical Testing
Sherry Laboratories

Test results relate only to the items tested. This document shall not be reproduced, except in full, without the written approval of Sherry Laboratories. The recording of false, fictitious, or fraudulent statements or entries on this document may be a punishable offense under federal and state law. The electronic transmittal of a report on services provided by Sherry Laboratories is at the request of the client. The transmittal is NOT the official report of Sherry Laboratories, but is provided for the convenience of the recipient. Sherry Laboratories is not liable for any degradation or changes in information in the transmittal. The official report of Sherry Laboratories will be provided on Sherry Laboratories letterhead in hard copy form and shall control for all purposes.



**SHERRY LABORATORIES
MIDSTATES**

INDIANA OKLAHOMA LOUISIANA

Tel: (918) 664-7768
Fax: (918) 664-5680
800-324-8378

Non-Metallics
825 E. 38th St.
Tulsa, OK 74145

LABORATORY REPORT

Attn: David Stanley
Raven Lining Systems
1024 North Lansing
Tulsa, OK 74106

Report No: 2000070105
Date Received: 07/07/2000
Date Reported: 07/11/2000
P.O. No: P 312416

Description: Raven 405.

TABER ABRASION TEST REPORT

Test Method: ASTM D4060-95
Pre-test Conditioning: None
Type of Wheel: CS17
Load/Wheel: 1000g
Speed: 70 rpm
Test Duration: 1000 cycles
Test Results:

| Panel No. | Weight loss after 1,000 cycles, mg | Weight loss, % |
|-----------|------------------------------------|----------------|
| 1 | 78.8 | 0.16 |

Approved by

Dan M. Lawson, Director
Non-Metallic Testing

Test results relate only to the items tested. This document shall not be reproduced, except in full, without the written approval of Sherry Laboratories Midstates. The recording of false, fictitious, or fraudulent statements or entries on this document may be a punishable offense under federal and state law.

“REDNER REPORT” LOS ANGELES COUNTY SANITATION DISTRICTS COATING EVALUATION STUDY

The County of Los Angeles conducting an evaluation process. utilized many protective systems protect concrete corrosive effects of environment. many of the had failed, in fact exhibited any at the beginning of



Sanitation Districts County has been evaluation of since 1985-86. Edward Esfandi are among those original report and The Districts had different types of over the years to structures from the the sanitary sewer Unfortunately protective systems only PVC liners degree of success this evaluation.

The focus of the evaluation was to evaluate protective coatings applied to corroded and uncorroded concrete. The purpose of the evaluation as to develop a list of suitable coatings and specifications for their application on new and rehabilitation projects.

The evaluation is conducted in precast concrete tanks (3' diameter x 2.5' deep). There is an inner and outer tank with the annular space being filled with water to simulate moisture from groundwater. The lower half of the inside tank is permitted to corrode for 6-8 weeks using a 10% sulfuric acid solution. Approximately 1" of corrosion typically results. This rate of corrosion is estimated at 15-20 times the highest rate of corrosion expected in actual service. After sufficient aggregate and even some reinforcing steel has been exposed, the coating manufacturer prepares and coats the corroded and uncorroded surfaces. 48 hours after the coating application, the tank is filled with water. 96 hours after application, concentrated sulfuric acid is added to the water for a final 10% acid concentration. The solution is drained and refilled on a quarterly basis for interim inspection. After one year the acid solution is removed and the evaluation is completed. The coatings are evaluated under three criteria: application, acid resistance and bonding characteristics. Over 60% of the coatings tested failed!

AquataPoxy and Raven coatings were tested and successfully passed this widely recognized evaluation. A full copy of the report is available upon request.



1 Workman Mill Road, Whittier, CA 90601-1998
2nd Address P.O. Box 4998, Whittier, CA 90607-4998
Phone: (310) 899-7411, FAX: (310) 993-8139

COUNTY SANITATION DISTRICTS OF LOS ANGELES COUNTY

QUALITY BY DESIGN
Chief Engineer and General Manager

February 22, 1994

EVALUATION OF PROTECTIVE COATINGS FOR CONCRETE

John A. Rehner, Sewerage System Superintendent, Randolph P. Hsi, Associate Engineer,
Edward J. Esfandi, Senior Engineer

February, 1994

County Sanitation Districts of Los Angeles County, Whittier California

Evaluation of Raven 405 Epoxy Coating for Concrete Protective Characteristics


Raven Chemicals' Raven 405 epoxy coating system was evaluated for its concrete protective characteristics in the Districts Concrete Coating and Liner Testing facilities in Compton for approximately one year of acid service. The coating system was well bonded to the concrete substrate. No indication of corrosion to the liner or the underlying concrete was observed.

As a result of this evaluation, Raven Chemicals' Raven 405 epoxy coating system will be included as an alternative coating product in specifications that we prepare in the future for concrete coating systems. Information contained in this letter is not for publication or advertisement. No endorsement is intended for this coating system. Prior written approval of the Sanitation Districts is required for any advertisement or promotion that involves this agency.

Thank you for your continued cooperation and interest in the Districts' evaluation program for concrete coatings. If you have any questions or need additional information, please contact Edward Esfandi at (310) 638-1161 ext. 222.

Very truly yours

Charles W. Carry


Edward J. Esfandi
Senior Engineer

EE:lg

INTRODUCTION

Concrete is the most widely used construction material in wastewater collection and treatment systems. Unfortunately, significant corrosion can occur to unprotected concrete when sulfide generation in wastewater is not controlled. Sources of sulfide in wastewater include: unregulated and/or uncontrolled industrial discharges, degradation of sulfur containing organic matter, or the microbiological reduction of sulfate or other oxidized forms of sulfur. The construction of regional collection and treatment systems has increased wastewater travel time in collection systems, culminating in anaerobic wastewater and consequently increased sulfide generation. Odors from manholes or wastewater treatment facilities create significant nuisance problems for most agencies. A major cause of odors is hydrogen sulfide, a gas detectable at extremely low concentrations. Hydrogen sulfide is notorious for its toxicity, as well as its ability to corrode a number of materials used in construction of sewers and treatment plants, including concrete. Concrete corrosion is caused by the aerobic microbial oxidation of hydrogen sulfide to sulfuric acid and the subsequent chemical reaction of the acid with the cement binder in the concrete. Most agencies are particularly sensitive to the nuisances created by the odor releases. Many agencies are often unaware of the significant corrosion occurring to their concrete facilities.

The County Sanitation Districts of Los Angeles County (Districts) have utilized different types of protective systems over the

years to minimize concrete corrosion. In the mid 1970's the use of vitrified clay liner places in the construction of large poured-in-place concrete sewers and inlet facilities proved unsuccessful. By the mid 1990's many epoxy coating systems were being tried. Inspections have documented coating failure wherever exposure to significant sulfuric acid attack occurred. Often any application flaws or coating failures are not easily noticed for several years. In the past ten years a considerable amount of marketing has developed for high solids fast cure coating systems. First hand experiences with these coating systems have resulted in widely different opinions from different agencies. One agency reports nothing but success, while another reports nothing but failure. Figure 1a and 1b illustrate the failure that occurred, after only 2 years of service, to a urethane coating applied to a drop manhole.

The only protective coating system that has developed any degree of success has been the application of polyvinyl chloride liners to concrete surfaces during construction. While this has become a standard specification for the Districts for new concrete construction, many questions remain concerning the best method and materials for rehabilitating existing corroded concrete structures. Many rehabilitation projects do not allow sufficient "down" time for conventional concrete surface repairs, using cementitious materials, followed by the application of liners. The application of a coating system that bonds to concrete and provides protection from microbial sulfuric acid would have wide application in the wastewater industry.

TESTING AND CERTIFICATION

Hydrostatic Head, Chemical Resistance and Adhesion Strength

Very few coatings routinely submit themselves for tough third party testing, much less pass the tests while setting standards that are unsurpassed. However, Aquatapoxy and Raven products are continually submitted and tested in industry recognized third party evaluations and testing. These photos are from a current study being conducted through the University of Houston in conjunction with the City of Houston. The testing objective is to evaluate whether or not coating products can be applied to damp concrete and withstand corrosive environments generally found in sewers. The coatings are applied to RCP while they are subjected to over 30' of hydraulic head pressure. AquataPoxy and Raven were also successfully tested for chemical attack and bond strength to dry and damp concrete and brick surfaces. Aquatapoxy and Raven have also successfully passed the industry recognized coating evaluation study conducted by the Los Angeles County Sanitation District.

Aquatapoxy A-6 and A-7 products also hold ANSI/NSF 61 certification for potable water applications and are acceptable under FDA and USDA guidelines for incidental food contact.



BOARD OF PUBLIC WORKS
MEMBERS

VALERIE LYNNE SHAW
PRESIDENT

ELLEN STEIN
VICE-PRESIDENT

JANICE WOOD
PRESIDENT PRO-TEMPORE

ADRIANA RUBALCAVA
COMMISSIONER

RONALD LOW
COMMISSIONER

JAMES A. GIBSON
SECRETARY

CITY OF LOS ANGELES
CALIFORNIA



JAMES K. HAHN
MAYOR

DEPARTMENT OF
PUBLIC WORKS

BUREAU OF
ENGINEERING

VITALY B. TROYAN, P.E.
CITY ENGINEER

650 SOUTH SPRING ST., SUITE 200
LOS ANGELES, CA 90014-1911

April 30, 2003

Joanne Hughes, Vice President
Raven Lining Systems
1024 North Lansing
Tulsa, Oklahoma 74106

Dear Ms. Hughes:

Re: CHEMICAL RESISTANCE TESTING OF RAVEN 405 EPOXY LINING

Attached is Lab No. 2003-514-91, dated April 10, 2003, showing the results of chemical resistance testing for the above maintenance hole product. The lining system responded to chemical exposure as follows:

*Weight change: **Excellent***

*Hardness change: **Excellent***

*Tensile strength change: **Excellent***

*Elongation: **Satisfactory**, with reactions to sulfuric acid, nitric acid, ferric chloride, detergent, biological and bleach exposures and a notable reaction to sodium hydroxide and ammonium hydroxide exposures.*

The lining system is identified as follows:

Trade Name: Raven 405

Approved Use: Sanitary Sewer Maintenance Rehabilitation

Installation: SSPWC Section 500-2 as modified by City of Los Angeles Brownbook

Resin: Blue-colored solid epoxy

The overall summary is that this material **passed** SSPWC Section 210-2.3 Chemical Resistance Test. To complete the evaluation process, a trail demonstration must be arranged where we may observe and verify an installation of the system. If you have any questions, please call me at (213)847-8776.

Sincerely,

Hugh S. Lee, Group Manager
Design Standards and Investigations Group
650 S. Spring Street, Suite 400
Los Angeles, California 90014-1913

<HSL:h/raven4.wpd>

Attachment (Lab No. 2003-514-91)

Chemical Resistance Test of
Raven Lining Systems
Raven 405 Blue
Epoxy Resin

Project Title: Maintenance Shaft & Sewer Rehabilitation
Project Number: BD001748
Engineer: Hugh Lee
Source: Raven Lining Systems
Date Received: 10/16/2002
Specification: SSPWC 210-2.3.3, 1997
Description: Raven 405 Blue Epoxy Resin

| SOLUTION | RESULTS CONDITIONED WEIGHT CHANGE % maximum | | | | REQUIREMENTS CONDITIONED WEIGHT CHANGE % |
|---|--|---------|---------|--------|--|
| | Days Immersion | | | | |
| | 28 | 56 | 84 | 112 | |
| <i>Sulfuric Acid, 20%</i> | 0.2239 | 0.3685 | 0.6617 | 0.6543 | All Solutions and Periods ± 1.5% max |
| <i>Sodium Hydroxide, 5%</i> | -0.0435 | 0.0532 | 0.1263 | 0.1700 | |
| <i>Ammonium Hydroxide, 5%</i> | 0.0231 | 0.1234 | 0.2410 | 0.2754 | |
| <i>Nitric Acid, 1%</i> | 0.0706 | 0.1708 | 0.3070 | 0.3531 | |
| <i>Ferric Chloride, 1%</i> | 0.0382 | 0.1305 | 0.2120 | 0.2824 | |
| <i>Soap, 0.1%</i> | 0.0351 | 0.1289 | 0.2087 | 0.2865 | |
| <i>Detergent, 0.1%</i> | 0.0222 | 0.1260 | 0.2322 | 0.2694 | |
| <i>BOD, ≥ 700ppm</i> | 0.0230 | 0.1314 | 0.2179 | 0.2889 | |
| <i>Bleach, 1%</i> | -0.0580 | -0.0988 | -0.3358 | 0.2835 | |
| <i>Sodium Hydroxide Buffer to PH 10</i> | 0.0203 | 0.1313 | 0.2182 | 0.2703 | |

Chemical Resistance Test of
Raven Lining Systems
Raven 405 Blue
Epoxy Resin

Project Title: Maintenance Shaft & Sewer Rehabilitation
 Project Number: BD001748
 Engineer: Hugh Lee
 Source: Raven Lining Systems
 Date Received: 10/16/2002
 Specification: SSPWC 210-2.3.3, 1997
 Description: Raven 405 Blue Epoxy Resin

| SOLUTION | RESULTS | REQUIREMENTS |
|-----------------------------------|---|----------------------------|
| | CONDITIONED HARDNESS CHANGE maximum 112 Days Immersion | |
| Sulfuric Acid, 20% | 1 | For Information Only |
| Sodium Hydroxide, 5% | 1 | |
| Ammonium Hydroxide, 5% | 2 | |
| Nitric Acid, 1% | 2 | |
| Ferric Chloride, 1% | 1 | |
| Soap, 0.1% | -1 | |
| Detergent, 0.1% | -3 | |
| BOD, ≥ 700ppm | 2 | |
| Bleach, 1% | -1 | |
| Sodium Hydroxide Buffer to PH 10 | -1 | |
| PHYSICAL PROPERTY | INITIAL RESULTS | |
| Hardness, Shore "D" ASTM D2240 | 85 | For Information Only |

Chemical Resistance Test of
Raven Lining Systems
Raven 405 Blue
Epoxy Resin

Project Title: Maintenance Shaft & Sewer Rehabilitation
 Project Number: BD001748
 Engineer: Hugh Lee
 Source: Raven Lining Systems
 Date Received: 10/16/2002
 Specification: SSPWC 210-2.3.3, 1997
 Description: Raven 405 Blue Epoxy Resin

| SOLUTION | RESULTS | | REQUIREMENTS |
|---|-----------------------|--------------|----------------------------|
| | Tensile Strength, psi | Elongation % | |
| | 112 Days Immersion | | |
| <i>Sulfuric Acid, 20%, Type I</i> | 8,974 | 1.7 | For Information Only |
| <i>Sodium Hydroxide, 5%, Type I</i> | 8,752 | 2.1 | |
| <i>Ammonium Hydroxide, 5%, Type I</i> | 8,428 | 1.8 | |
| <i>Nitric Acid, 1%, Type I</i> | 8,698 | 1.7 | |
| <i>Ferric Chloride, 1%, Type I</i> | 8,907 | 1.8 | |
| <i>Soap, 0.1%, Type I</i> | 8,615 | 1.6 | |
| <i>Detergent, 0.1%, Type I</i> | 8,568 | 1.7 | |
| <i>BOD, ≥ 700ppm, Type I</i> | 8,668 | 1.7 | |
| <i>Bleach, 1%, Type I</i> | 8,395 | 1.7 | |
| <i>Sodium Hydroxide Buffer to PH 10, Type I</i> | 8,540 | 1.7 | |
| PHYSICAL PROPERTIES | INITIAL RESULTS | | |
| <i>Initial Tensile Strength, psi</i> | 9,034 | | For Information Only |
| <i>Initial Elongation, %</i> | 1.5 | | |

Chemical Resistance



Raven 405 coating has been immersion tested for a minimum of six (6) months according to ASTM D543 (modified) Standard Practices for Evaluating the Resistance of Plastics to Chemical Reagents. The results indicate classification of Raven 405 as being suitable for constant immersion duty in the following reagents:

- Water
- Nitric Acid, 5%
- Phosphoric Acid, 10%
- Sulfuric Acid, 20%
- Sodium Hydroxide, 10%
- Unleaded Gasoline
- Vegetable Oil
- Detergent Solution, 0.1%
- Soap Solution, 0.1%

During the course of testing, none of the specimens exhibited weight loss, spalling, cracking or blistering. Immersion samples are “free” coatings without concrete or brick substrates, immersing over twice the area that would normally see service. Color change was a very slight orange surface coloration for the sample immersed in Nitric Acid and a slight darkening of the sample immersed in the Sulfuric Acid. No degradation was experienced.

For additional chemical resistance performance of Raven 405, see the Raven Chemical Resistance Chart or contact Raven with project details at 800-324-2810.